



## LEKOLED TECHNOLOGY CORPORATION

# TEST REPORT

Prepared For:	LEKOLED TECHNOLOGY CORPORATION 3rd Floor, First Building WeiQun Industrial Park, BaiHua Community, GuangMing District, Shenzhen, Guangdong, China
Product Name:	SMD LED
Model Number:	0.2W 5050 SMD
Prepared By:	Shenzhen BST Technology Co., Ltd.  Building No.23-24, Zhiheng industrial park, Guankouer Road, Nantou, Nanshan District, Shenzhen, Guangdong, China.
Test Date:	May. 29, 2017-Feb. 13, 2018
Date of Report:	Feb. 26, 2018
Report No.:	BST1706804480002SR-2



Shenzhen BST Technology Co., Ltd.

Report No.: BST1706804480002SR-2

## TEST REPORT

### LUMEN MAINTENANCE TESTING ACCORDING TO THE IESNA LM-80-08 TEST STANDARD

<b>Testing laboratory</b> .....	: Shenzhen BST Technology Co., Ltd.
<b>Address</b> .....	: Building No.23-24, Zhiheng industrial park, Guankouer Road, Nantou,Nanshan District, Shenzhen, Guangdong, China.
<b>Testing location</b> .....	: Shenzhen BST Technology Co., Ltd.
<b>Applicant</b> .....	: LEKOLED TECHNOLOGY CORPORATION
<b>Address</b> .....	: 3rd Floor,First Building WeiQun Industrial Park,BaiHua Community,GuangMing District, Shenzhen, Guangdong, China
<b>Standard</b>	: IESLM-80-08
<b>Non-standard test method</b> .....	: N.A.
<b>Type of test object</b> .....	: SMD LED
<b>Trademark</b> .....	: LKL
<b>Model/type reference</b> .....	: 0.2W 5050 SMD
<b>Rating</b> .....	: 2.7-2.9V—, 60mA ,0.2W CCT:3000K
<b>Manufacturer</b> .....	: LEKOLED TECHNOLOGY CORPORATION
<b>Address</b> .....	: 3rd Floor,First Building WeiQun Industrial Park,BaiHua Community,GuangMing District, Shenzhen, Guangdong, China



Shenzhen BST Technology Co., Ltd.

Report No. : BST1706804480002SR-2

Name and address of the testing laboratory: Shenzhen BST Technology Co., Ltd. Building No.23-24, Zhiheng industrial park, Guankouer Road, Nantou, Nanshan District, Shenzhen, Guangdong, China

Prepared by :

*Tracy Yang*

Engineer

Reviewer:

*Owen*

Supervisor

Approved & Authorized Signer:



**Possible test case verdicts :**

Test case does not apply to the test object..... : N(.A.)

Test object does meet the requirement..... : P(ass)

Test object does not meet the requirement..... : F(ail)

**General remarks:**

**Throughout this report a point is used as the decimal separator. The test results presented in this report relate only to the object tested.**



**Test Results Summary:**

Summary	I	II	III
<b>Condition</b>	Ts=55°C TA=54.5°C R.H <65% If=60mA	Ts=85°C TA=84.4°C R.H.<65% Ip=60mA	Ts=104.9°C TA=103.9°C R.H.<65% If=60RIA
<b>Duration(hour)</b>	6000	6000	6000
<b>Interval(hour)</b>	0,1000,2000,3000,4000, 5000,6000	0,1000,2000,3000,4000, 5000, 6000	0,1000,2000,3000,4000, 5000,6000
<b>Sample number</b>	20	20	20
<b>Average Lumen Maintenance at 6000 hour</b>	96.72%	96.25%	95.67%
<b>Average Chromaticity Shift Δu'v' at 6000 hour</b>	0.0026	0.0029	0.0031
<b>Failure</b>	None	None	None
<b>α</b>	7.321 E-06	7.769E-06	9.487E-06
<b>β</b>	1.011	1.008	1.013
<b>Calculated L70(6k) (hours)</b>	50,000	47,000	39,000
<b>Reported TM-21 L70 Lifetime:</b>	>36,000	>36,000	>36,000

**Equipments Used for Testing:**

Equipment	Model	Equipment No.
DC Power Supply	IT6122	BSTNX001
Power meter	WT210	BSTNX001
Spectroradiometer	SPEC300	BN067
0.3m Integrating Sphere	—	BSTNX002

**Test Data:****Operating Condition: 55°C/60mA**

Sample No.	VF(V)	LF(lm)	Lumen Maintenance (%)					
	Ohr(Initial)		1000hrs	2000hrs	3000hrs	4000hrs	5000hrs	6000hrs
1	2.78	28.54	100.30	99.89	99.12	98.56	97.53	96.93
2	2.73	29.59	100.05	99.64	98.81	97.73	96.80	95.85
3	2.81	28.54	100.26	99.98	98.82	98.20	97.95	96.84
4	2.79	29.51	100.13	99.74	98.65	97.85	96.69	95.92
5	2.74	30.00	100.02	99.81	98.85	97.82	97.15	96.84
6	2.85	28.88	99.89	98.94	98.76	97.07	97.04	96.88
7	2.76	29.16	102.81	101.92	100.13	99.73	98.27	97.38
8	2.84	29.51	99.71	99.45	98.89	97.91	97.18	96.94
9	2.82	28.62	100.02	99.39	99.15	98.51	97.80	97.62
10	2.77	28.53	99.90	99.29	98.51	98.06	97.61	96.81
11	2.82	28.54	99.87	98.60	98.33	97.92	96.83	96.25
12	2.87	29.32	100.40	99.73	99.01	98.54	98.28	97.83
13	2.79	29.59	100.03	99.55	98.92	98.26	97.44	96.86
14	2.71	28.54	99.94	98.73	98.52	98.05	97.31	96.63
15	2.76	29.29	101.44	100.03	99.69	98.77	97.82	96.58
16	2.77	30.00	99.95	99.74	98.46	97.81	96.75	95.82
17	2.78	28.78	100.21	99.87	98.79	97.34	97.62	96.64
18	2.83	29.16	100.16	99.30	98.64	97.32	96.99	96.11
19	2.85	29.37	100.13	99.92	98.74	98.25	97.93	96.83
20	2.83	28.62	100.18	100.02	99.28	98.84	97.82	96.82
<b>Avg.</b>	2.80	29.10	100.27	99.68	98.90	98.13	97.44	96.72
<b>Median</b>	2.79	29.16	100.09	99.74	98.82	98.06	97.49	96.83
<b>σ</b>	0.043	0.489	0.674	0.655	0.414	0.590	0.487	0.525
<b>Min.</b>	2.71	28.53	99.71	98.60	98.33	97.07	96.69	95.82
<b>Max.</b>	2.87	30.00	102.81	101.92	100.13	99.73	98.28	97.83

**Operating Condition: 55°C/60mA**

No.	CCT(K)	Chromaticity Shift $\Delta u'v'$					
	Oh(Initial)	1000hrs	2000hrs	3000hrs	4000hrs	5000hrs	6000hrs
1	3005	0.0010	0.0011	0.0012	0.0017	0.0017	0.0021
2	2929	0.0011	0.0012	0.0015	0.0021	0.0023	0.0023
3	3074	0.0010	0.0012	0.0021	0.0023	0.0017	0.0021
4	2916	0.0009	0.0012	0.0026	0.0029	0.0032	0.0032
5	2941	0.0012	0.0016	0.0015	0.0020	0.0027	0.0030
6	2930	0.0010	0.0009	0.0015	0.0020	0.0022	0.0023
7	3055	0.0010	0.0012	0.0013	0.0020	0.0022	0.0022
8	3058	0.0007	0.0012	0.0011	0.0017	0.0021	0.0022
9	2964	0.0008	0.0011	0.0011	0.0017	0.0020	0.0022
10	2939	0.0009	0.0014	0.0012	0.0019	0.0024	0.0026
11	3093	0.0010	0.0012	0.0013	0.0019	0.0022	0.0026
12	3078	0.0009	0.0013	0.0014	0.0019	0.0021	0.0024
13	3032	0.0012	0.0012	0.0030	0.0034	0.0037	0.0040
14	3065	0.0010	0.0015	0.0017	0.0021	0.0022	0.0025
15	2951	0.0006	0.0010	0.0015	0.0018	0.0023	0.0027
16	2963	0.0010	0.0011	0.0014	0.0021	0.0025	0.0027
17	2950	0.0009	0.0012	0.0015	0.0020	0.0027	0.0030
18	2931	0.0008	0.0016	0.0011	0.0015	0.0020	0.0021
19	2977	0.0010	0.0013	0.0015	0.0021	0.0026	0.0029
20	3004	0.0013	0.0011	0.0016	0.0023	0.0025	0.0028
<b>Average</b>	2993	0.0010	0.0012	0.0016	0.0021	0.0024	0.0026
<b>Median</b>	2971	0.0010	0.0012	0.0015	0.0020	0.0023	0.0026
$\delta$	58.26	0.0002	0.0002	0.0005	0.0004	0.0005	0.0005
<b>Min.</b>	2916	0.0006	0.0009	0.0011	0.0015	0.0017	0.0021
<b>Max.</b>	3093	0.0013	0.0016	0.0030	0.0034	0.0037	0.0040



Operating Condition: 85°C/60mA

Sample No.	VF(V)	LF(lm)	Lumen Maintenance (%)					
	0hr(Initial)		1000hrs	2000hrs	3000hrs	4000hrs	5000hrs	6000hrs
1	2.76	28.54	99.98	98.71	97.49	96.74	96.32	96.01
2	2.77	28.59	100.23	99.73	98.60	97.84	96.83	95.93
3	2.73	29.54	100.91	99.80	98.59	97.39	96.74	95.46
4	2.84	29.51	99.96	99.21	98.70	97.57	97.10	96.83
5	2.81	30.00	100.50	99.83	98.65	98.20	97.45	96.73
6	2.83	28.57	99.95	99.30	98.55	97.39	97.03	96.84
7	2.78	29.16	100.10	99.47	98.75	97.81	97.46	96.67
8	2.81	29.51	99.79	99.62	98.91	98.24	97.65	97.52
9	2.76	28.82	99.88	98.74	98.05	97.62	96.46	96.32
10	2.73	28.53	99.92	98.45	97.68	97.04	96.68	96.22
11	2.75	29.54	100.13	99.28	98.73	97.34	97.01	96.65
12	2.73	29.59	99.67	98.47	98.01	97.73	96.81	95.47
13	2.85	28.54	100.03	99.91	99.19	98.42	97.35	96.73
14	2.82	29.51	99.60	99.07	98.65	97.99	97.51	96.59
15	2.78	30.00	99.89	99.30	98.87	98.24	97.52	96.08
16	2.78	28.48	99.89	99.30	98.90	97.07	96.96	95.37
17	2.76	29.16	99.97	99.65	98.90	97.90	97.39	96.0
18	2.77	29.51	99.79	98.19	97.54	97.27	95.34	95.16
19	2.78	28.96	99.87	99.87	98.94	97.73	96.18	95.52
20	2.76	28.09	100.20	99.89	99.30	98.90	97.07	96.96
<b>Avg.</b>	2.78	29.11	100.01	99.29	98.55	97.72	96.94	96.25
<b>Median</b>	2.78	29.16	99.96	99.30	98.68	97.73	97.02	96.27
<b>σ</b>	0.035	0.544	0.285	0.519	0.508	0.511	0.548	0.620
<b>Min.</b>	2.73	28.09	99.60	98.19	97.49	96.74	95.34	95.16
<b>Max.</b>	2.85	30.00	100.91	99.91	99.30	98.90	97.65	97.52



**Operating Condition: 85°C/60mA**

No.	CCT(K)	Chromaticity Shift $\Delta u'v'$					
	Oh(Initial)	1000hrs	2000hrs	3000hrs	4000hrs	5000hrs	6000hrs
1	2997	0.0007	0.0011	0.0013	0.0023	0.0026	0.0029
2	2943	0.0007	0.0012	0.0014	0.0020	0.0023	0.0026
3	2994	0.0010	0.0015	0.0017	0.0024	0.0027	0.0033
4	3005	0.0012	0.0012	0.0017	0.0023	0.0027	0.0029
5	3051	0.0011	0.0011	0.0017	0.0023	0.0026	0.0027
6	3055	0.0011	0.0012	0.0015	0.0021	0.0024	0.0026
7	2990	0.0013	0.0020	0.0026	0.0033	0.0035	0.0037
8	2929	0.0013	0.0013	0.0020	0.0025	0.0032	0.0034
9	3083	0.0012	0.0013	0.0016	0.0023	0.0028	0.0031
10	3031	0.0014	0.0012	0.0015	0.0022	0.0026	0.0030
11	3084	0.0012	0.0013	0.0017	0.0023	0.0030	0.0032
12	3083	0.0012	0.0011	0.0014	0.0020	0.0027	0.0031
13	3059	0.0012	0.0009	0.0014	0.0020	0.0023	0.0029
14	3065	0.0013	0.0016	0.0014	0.0018	0.0021	0.0023
15	3003	0.0010	0.0013	0.0017	0.0020	0.0021	0.0022
16	3065	0.0012	0.0016	0.0016	0.0023	0.0027	0.0028
17	3037	0.0013	0.0018	0.0021	0.0028	0.0027	0.0032
18	3036	0.0011	0.0013	0.0020	0.0025	0.0028	0.0030
19	3085	0.0011	0.0014	0.0016	0.0022	0.0024	0.0027
20	3024	0.0014	0.0014	0.0016	0.0023	0.0026	0.0029
<b>Average</b>	3031	0.0012	0.0013	0.0017	0.0023	0.0026	0.0029
<b>Median</b>	3037	0.0012	0.0013	0.0016	0.0023	0.0027	0.0029
$\bar{\sigma}$	44.23	0.0002	0.0003	0.0003	0.0003	0.0003	0.0003
<b>Min.</b>	2929	0.0007	0.0009	0.0013	0.0018	0.0021	0.0022
<b>Max.</b>	3085	0.0014	0.0020	0.0026	0.0033	0.0035	0.0037

**Operating Condition: 105°C/60mA**

Sample No.	VF(V) LF(lm)		Lumen Maintenance (%)					
	Ohr(Initial)		1000hrs	2000hrs	3000hrs	4000hrs	5000hrs	6000hrs
1	2.84	28.19	100.05	99.68	98.55	97.21	96.91	95.99





Shenzhen BST Technology Co., Ltd.

Report No.: BST18021047090002SR-2

<b>2</b>	2.76	28.61	99.87	99.51	98.54	98.14	97.06	96.33
<b>3</b>	2.76	28.42	101.21	100.52	99.54	98.17	97.82	96.27
<b>4</b>	2.85	29.97	100.13	99.76	98.62	97.14	96.17	95.47
<b>5</b>	2.82	30.00	99.87	99.63	98.46	97.07	96.98	96.13
<b>6</b>	2.81	29.63	99.92	99.66	98.55	97.25	96.24	95.45
<b>7</b>	2.76	29.49	100.12	99.63	98.56	97.04	96.85	95.71
<b>8</b>	2.84	29.11	100.07	99.58	98.74	98.36	97.26	96.37
<b>9</b>	2.83	28.69	99.87	99.55	98.61	97.27	97.02	96.16
<b>10</b>	2.79	28.87	99.92	99.63	98.59	97.05	95.91	95.27
<b>11</b>	2.85	29.62	99.87	99.60	98.73	97.25	96.18	95.18
<b>12</b>	2.75	28.18	100.05	99.73	98.52	97.07	96.64	95.54
<b>13</b>	2.81	28.36	99.97	99.28	98.72	97.26	96.09	95.16
<b>14</b>	2.84	29.95	100.07	99.52	98.53	97.43	96.83	95.65
<b>15</b>	2.75	28.08	100.13	99.68	98.41	97.12	96.29	95.40
<b>16</b>	2.82	29.84	99.97	99.60	98.64	97.23	96.17	95.23
<b>17</b>	2.79	29.55	99.97	99.69	98.67	97.20	96.76	95.63
<b>18</b>	2.77	28.54	99.92	99.68	98.60	97.15	96.12	95.22
<b>19</b>	2.73	28.47	99.97	99.59	98.51	97.08	96.08	95.35
<b>20</b>	2.74	29.78	100.84	99.52	98.62	97.26	96.19	95.80
<b>Avg.</b>	2.80	29.07	100.09	99.65	98.64	97.34	96.58	95.67
<b>Median</b>	2.80	28.99	99.97	99.63	98.60	97.22	96.47	95.59
<b>σ</b>	0.039	0.674	0.329	0.223	0.224	0.385	0.493	0.400
<b>Min.</b>	2.73	28.08	99.87	99.28	98.41	97.04	95.91	95.16
<b>Max.</b>	2.85	30.00	101.21	100.52	99.54	98.36	97.82	96.37



Shenzhen BST Technology Co., Ltd.

Report No.: BST18021047090002SR-2

**Operating Condition: 105°C/60mA**

No.	CCT(K)	Chromaticity Shift $\Delta u'v'$					
	Oh(Initial)	1000hrs	2000hrs	3000hrs	4000hrs	5000hrs	6000hrs
1	3080	0.0014	0.0016	0.0018	0.0021	0.0025	0.0027
2	2934	0.0012	0.0015	0.0020	0.0027	0.0030	0.0034
3	2996	0.0011	0.0016	0.0018	0.0022	0.0026	0.0028
4	2983	0.0010	0.0011	0.0012	0.0017	0.0021	0.0026
5	3036	0.0011	0.0012	0.0015	0.0021	0.0023	0.0027
6	3032	0.0020	0.0024	0.0032	0.0034	0.0036	0.0040
7	3007	0.0018	0.0022	0.0030	0.0032	0.0034	0.0039
8	3061	0.0018	0.0022	0.0025	0.0027	0.0034	0.0036
9	3080	0.0020	0.0024	0.0026	0.0028	0.0030	0.0034
10	3034	0.0018	0.0020	0.0024	0.0026	0.0028	0.0030
11	3095	0.0014	0.0016	0.0023	0.0023	0.0024	0.0026
12	3086	0.0016	0.0018	0.0022	0.0024	0.0023	0.0029
13	3040	0.0012	0.0015	0.0022	0.0025	0.0028	0.0031
14	2956	0.0013	0.0016	0.0019	0.0024	0.0025	0.0028
15	2916	0.0012	0.0014	0.0021	0.0023	0.0025	0.0027
16	2962	0.0013	0.0015	0.0022	0.0022	0.0028	0.0031
17	2939	0.0013	0.0014	0.0021	0.0024	0.0025	0.0029
18	2934	0.0013	0.0016	0.0021	0.0025	0.0026	0.0032
19	2985	0.0014	0.0016	0.0022	0.0024	0.0028	0.0032
20	2969	0.0013	0.0016	0.0021	0.0025	0.0027	0.0033
<b>Average</b>	3006	0.0014	0.0017	0.0022	0.0025	0.0027	0.0031
<b>Median</b>	3002	0.0013	0.0016	0.0022	0.0024	0.0027	0.0031
<b>6</b>	55.52	0.0003	0.0004	0.0004	0.0004	0.0004	0.0004
<b>Min.</b>	2916	0.0010	0.0011	0.0012	0.0017	0.0021	0.0026
<b>Max.</b>	3095	0.0020	0.0024	0.0032	0.0034	0.0036	0.0040



## In situ Temperature and Driver Current Measurements of Final Product

## 1.1 Reference Standard

ANSI/UL 8750-2009: Standard for Light Emitting Diode (LED) Equipment for Use in Lighting Products

ANSI/UL 153-2002: Standard for Safety of Portable Electric Luminaires

ANSI/UL 1598-2008: Standard for Safety of Luminaires

## 1.2 Test Equipment

Device	Manufacture	Model No	Serial No	Cal Due
AC Power Source	ALL POWER	APW-110N	992257	2018-08-28
Digital Power Meter	YOKOGAWA	WT310	C2QM02030V	2018-08-30
Hybrid Recorder (60 channel)	AGILENT	34970A	MY41009304	2018-09-13


Statement of Traceability: Shenzhen BST Technology Co., Ltd. that all calibration has been performed using suitable standards traceable to National Primary Standards and International System of Units (SI).

1.3 - Temperature Measurement Data The sample was operated until constant temperatures were obtained, temperature was considered constant if the sample was operating for at least three hours and upon three A successive readings - taken at 15 minute intervals - were within one degree and were not rising. Thermocouples were attached at locations described in the results by means of a cement made of water glass and Fuller's earth, solder, or epoxy.

Ambient Temperature. °C: 25±5°CRelative Humidity, % : 56 %


Supply voltage: 120 V 60 Hz Type of thermocouples: K

Temperature measurement point of [Ts]:

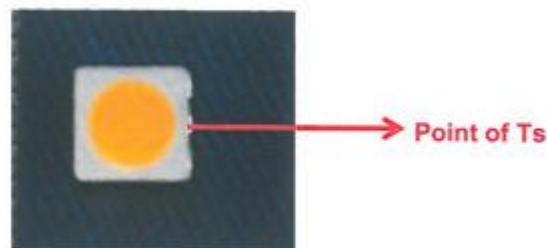



**ANNEX:**

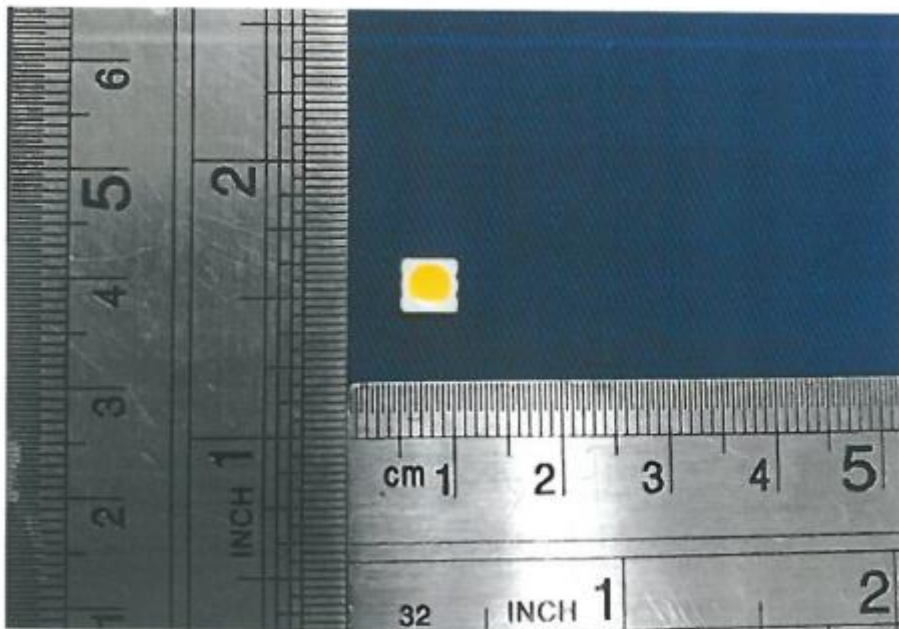

**Photo-documentation**